

222 Cavalcade Street, 77009-3213
P.O. Box 8768, Houston, Texas 77249-8768
Tel: (713) 692-9151 Fax: (713) 696-6205

Attention: J'Lynn Hare

Rumber Materials, Inc.

621 West Division Street

Muenster, TX 76252

P: 940-759-4181 / F: 940/759-4011

W/O. No.: RUM004-10-19-35775-3

P.O. No.:

Report Date: 10/26/2007


Rumber Boards – Plain vs. Fiberwrap

Identification: 9404 Boards

Description: 1-3/4" x 8-1/8" tested on 18" beam centers

Plain Board		Fiberwrap	
Load (lbs)	Deflection (in.)	Load (lbs)	Deflection (in.)
840	0.052	840	0.085
1,510	0.132	1,510	0.165
2,040	0.268	2,040	0.255
2,850	0.464	2,850	0.370
3,550	0.735	3,550	0.517
4,080	1.115	3,655	0.550

Loading was stopped at 3,655 lbs. at beginning of separation and cracking of fiberwrap

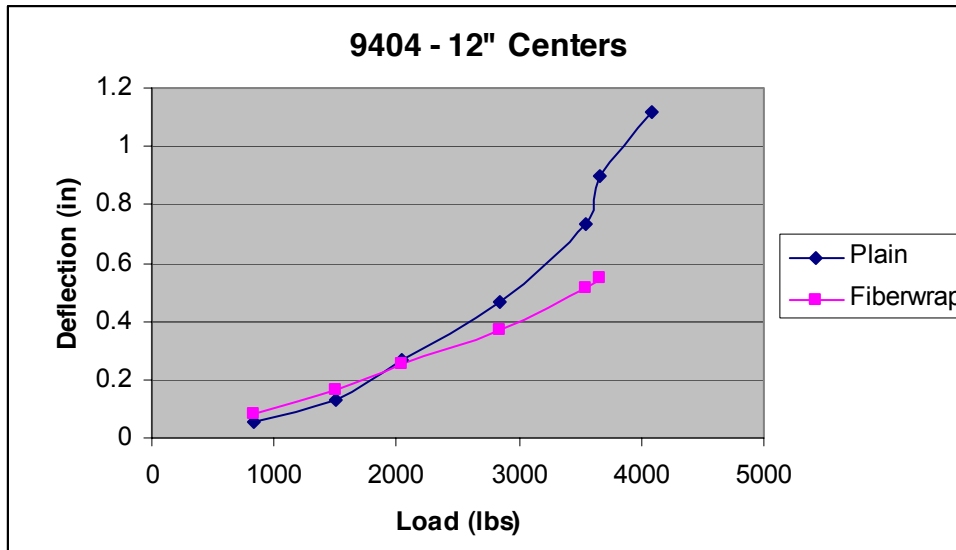

Our letters and reports are for the exclusive use of the client to whom they are addressed and shall not be reproduced except in full without the approval of the testing laboratory. The use of our name must receive our written approval. Our letters and reports apply only to the sample tested and/or inspected, and are not indicative of the quantities of apparently identical or similar products. Material submitted to our metals department will be discarded after a period of 30 days unless otherwise directed. Stork SWL, is an operating unit of Stork Materials Technology B.V., Amsterdam, The Netherlands, which is a member of the Stork group

Respectfully Submitted

Terry Wilt
Terry Wilt
Manager, Product Evaluation